

## A NEW METHOD FOR SYNTHESIS OF CdTe NANOPARTICLES BY LASER RADIATION

M.A. JAFAROV<sup>2</sup>, V.M. SALMANOV<sup>2</sup>, A.G. GUSEINOV<sup>1,2</sup>, G.B. IBRAGIMOV<sup>1,2</sup>,  
R.M. MAMEDOV<sup>2</sup>, T.A. MAMEDOVA<sup>2</sup>, F.Sh. AKHMEDOVA<sup>2</sup>

<sup>1</sup>*Institute of Physics, Ministry of Science and Education of the Republic of Azerbaijan*

*AZ 1143, G. Javid Avenue 131, Baku, Azerbaijan*

<sup>2</sup>*Baku State University, AZ1148 Baku, Azerbaijan*

*e-mail: vagif\_salmanov@yahoo.com*

The synthesis of CdTe nanoparticles using CdCl<sub>2</sub> and TeO<sub>2</sub> solutions under the action of laser radiation was experimentally studied. The radiation source was a pulsed Nd:YAG laser with built-in generators of the 2nd and 3rd harmonics, designed to generate radiation with a wavelength of 1064, 532, and 335 nm. The laser pulse duration was 10 ns with an energy of 135 mJ per pulse. In a colloidal solution, the formation of nanoparticles with a diameter of 10 to 50 nm was observed. X-ray diffraction analysis established that the crystal structure of the nanoparticles is the same as that of the bulk material (hexagonal). It is shown that the photoluminescence emission of the obtained nanoparticles has a green color (~510 nm) and is associated with the radiative recombination of free excitons.

**Keywords:** CdTe nanoparticles, laser ablation, photoluminescence.

**PACS:** 78.20.-e; 78.40.-q

### 1. INTRODUCTION

Among the most common semiconductor nanoparticles of groups II–VI, CdTe nanocrystals are of great interest for applications in optoelectronics, solar cells, LEDs, and biology [1–5]. Due to the developed surface (in a 1 nm particle, almost all atoms are surface atoms) and the manifestation of the quantum confinement effect [6], nanosized semiconductors have unique optical, electronic, catalytic, and other properties that are attractive to researchers. For example, solar cells based on nanosized cadmium telluride demonstrate a record efficiency of solar energy conversion and are currently considered more promising for mass application compared to traditional silicon batteries [7, 8]. To obtain nanoclusters and nanostructured materials, various methods are used - gas-dynamic, chemical, plasma, beam [9-18]. CdTe nanocrystals in solution are most often obtained by chemical synthesis using organometallic "precursors". These methods provide nearly monodisperse nanocrystals that exhibit narrow photoluminescence emission (up to ~30 nm) as well as high quantum yields. However, in general they require the use of expensive, pyrophoric, hazardous chemical precursors, as well as high temperatures and long reaction times.

One of the most promising methods for the synthesis of clusters is pulsed laser ablation (PLA) [1, 4]. Its main advantage is the ability to exclude the presence of foreign impurities in synthesized nanostructures, which is especially important for applications (one foreign atom in a 2 nm particle corresponds to a defect concentration of ~10<sup>21</sup> cm<sup>-3</sup> and can significantly change its properties). The advantages of the PLA method also include its flexibility and the ability to control the process of cluster growth. The formation of nanoclusters during PLA can occur according to two different scenarios: aggregation of the initial ablation products (atoms,

molecules) in an expanding laser plasma and direct emission from the irradiated surface. Recently, significant progress has been made in the PLA synthesis of single-component semiconductor nanoclusters with controlled size, shape, and optical properties [19, 20], as well as in the understanding and quantitative description of the cluster formation process [21–23]. Laser ablation of nanoparticles in a liquid has attracted great interest due to its simplicity, the absence of the need for surfactants, and good control of the size and shape of synthesized nanoparticles [24-27]. In this method, many parameters, such as laser radiation flux density, laser radiation wavelength, pulse duration, and type of colloidal solution, can affect the characteristics of synthesized nanoparticles.

It should be noted that in all the above works devoted to laser ablation, bulk CdTe crystals grown by the Bridgman method were used as target materials. Laser ablation was carried out either in a vacuum or by immersing the target in various liquids, using ultrashort nano and femtosecond laser pulses. Indeed, the synthesis of CdTe nanoparticles by laser ablation, as noted, has great advantages over other methods. However, it should be taken into account that this method requires the growth of undoped CdTe crystals, which is by no means a simple technological problem. In this work, we propose a new method for obtaining nanoparticles, direct interaction of laser radiation with solutions that make up the components of CdTe nanoparticles. As shown by our experimental studies, the structural characteristics and optical properties of CdTe nanoparticles are significantly superior to those of nanoparticles obtained using a solid target.

### 2. EXPERIMENTAL METHODS

CdTe nanoparticles were synthesized in solution using the reactive laser ablation method. Highly pure CdCl<sub>2</sub> and TeO<sub>2</sub> powders mixed with distilled water

were used as initial raw materials. The reaction proceeded according to the following formula:



Immediately after irradiation with a laser pulse, CdTe nanoparticles were formed. The ablation process was performed by laser radiation with a wavelength of  $\lambda=1064$  nm, with a pulse energy of 135 mJ and an ablation time of  $\sim 10$  min. The radiation source was a pulsed Nd:YAG laser with built-in generators of the 2nd and 3rd harmonics, designed to generate radiation

with a wavelength of 1064, 532, and 335 nm. The laser pulse duration was 10 ns with a maximum power of  $\sim 12$  MW/cm<sup>2</sup>. The radiation intensity was varied using calibrated neutral light filters. The optical absorption and luminescence spectra of CdTe nanoparticles were studied using an automatic M833 double dispersion monochromator (spectral resolution  $\sim 0.024$  nm at a wavelength of 600 nm), with computer control and a detector that records radiation in the wavelength range of 350–2000 nm. The scheme of the experimental setup is shown in fig.1.

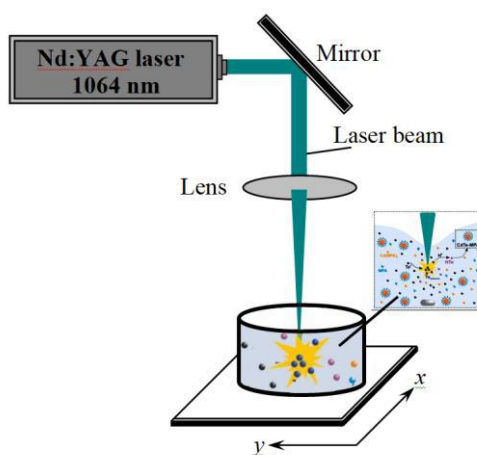


Fig. 1. Diagram of the experimental setup for ablation of GaSe nanoparticles.

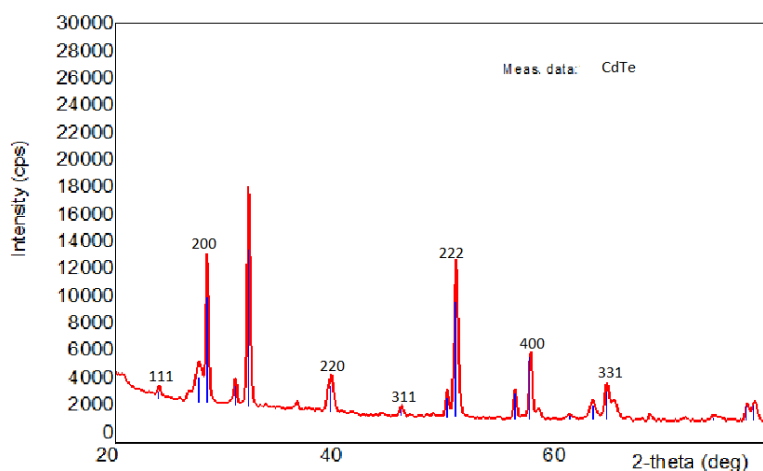


Fig. 2. Diffraction pattern (XRD) of CdTe nanoparticles on a glass substrate.

On figure 2 shows the diffraction pattern (XRD) of nanoparticles from drops of a CdTe colloidal solution dried on a clean glass substrate. CuK  $\alpha$ ,  $\lambda=1.544178\text{A}^0$  SSFOM: F17-610.0.5.10.60 were used as the radiation source.

It is shown that the diffraction planes (111), (200), (220), (311), (222), (400), (331), (422), and (511) at  $2\theta$  diffraction angles  $23.62^\circ$ ,  $27.89^\circ$ ,  $38.97^\circ$ ,  $45.28^\circ$ ,  $49.34^\circ$ ,  $56.75^\circ$ ,  $63.60^\circ$ ,  $73.22^\circ$ , and  $76.84^\circ$ , respectively, correspond to the cubic (zinc blende) structure of the bulk CdTe crystal [28], which confirms the crystal structure of the synthesized nanoparticles, which is the same as that of the bulk material.

Based on the X-ray diffraction patterns, using the Debye–Scherer formula [29], the sizes of the obtained nanoparticles were calculated:

$$D = \frac{k\lambda}{\beta \cos\theta} \quad (2)$$

where  $D$  – sizes of nanoparticles,  $k = 0.9$  – line shape factor (shape factor),  $\beta = 0.035 \text{ A}^0$  – intensity maximum half-width (FWHM- Full Width at Half Maximum),  $\lambda = 1.54 \text{ A}^0$ ,  $\theta$  – Bragg angle,  $\cos\theta=0.727$ . Estimates show that the average size of CdTe crystallites is 27.434 nm (see Table 1).

Table 1.

Sizes of CdTe crystallites calculated using the Debye–Scherer formula

2 theta	Crystallite size
23.62(3) 111	28.27 nm
27.891(9) 200	34.91 nm
38.97(3) 220	16.31 nm
45.28(5) 311	23.66 nm
49.347(14) 222	39.72 nm
56.75(8) 400	47.17 nm
63.60(5) 331	20.78 nm
73.2(2) 422	10.87 nm
76.84(3) 511	25.22 nm
average crystallite size:	27.434 nm

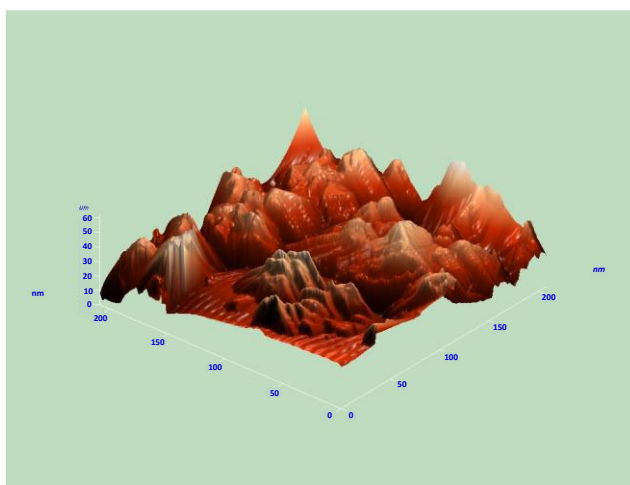


Fig. 3. AFM image of CdTe nanoparticles on a glass substrate.

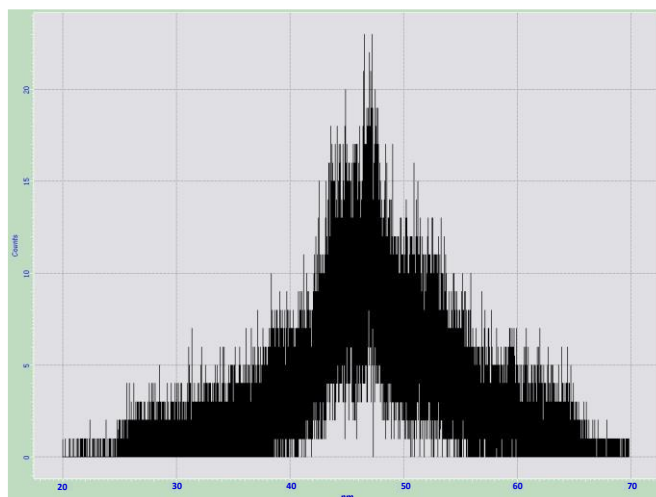


Fig.4. Histogram of particle size distribution.

The surface morphology of the synthesized CdTe nanoparticles was studied using AFM analysis. Figure 3 shows a 3D AFM image of CdTe nanoparticles on a glass substrate. As can be seen from the figure, a homogeneous distribution of particles in the presented figure is not observed.

The histogram of particle size distribution is shown in fig. 4. The average particle size estimated

using the software was about 40-50 nm. The particle size value is higher than calculated by X-ray diffraction analysis. This is due to the fact that XRD depends on the free volume of dimensional defects, while AFM directly visualizes the grain without taking into account the degree of defectiveness of the crystal.

The absorption curve from a colloidal solution of

CdTe nanoparticles is shown in Figure 5a. The onset of absorption at ~500 nm is consistent with the absorption of an ensemble of nanoparticles whose maximum diameter is ~50 nm. Taking into account that CdTe is a semiconductor with a direct band gap, from dependence  $\alpha^2 \sim f(h\nu)$ , the band gap of the studied samples was determined, which turned out to be equal to  $E_g=2.46$  eV (Fig. 5b). This value is 0.97

eV larger than the band gap of a bulk undoped CdTe crystal, ( $E_g=1.49$  eV (~827 nm) [1]). It should be noted that the shift of the red absorption band of nanoparticles to the short-wavelength region of the spectrum compared to a bulk crystal is a characteristic feature semiconductor nanoparticles, which is associated with the quantum size effect.

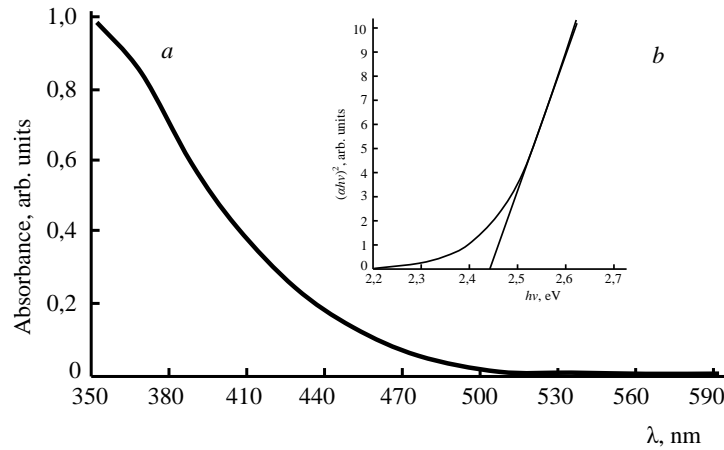


Fig. 5. Optical absorption spectrum (a) and  $\alpha^2 \sim f(h\nu)$  dependence (b) of CdTe nanoparticles obtained in a colloidal solution.

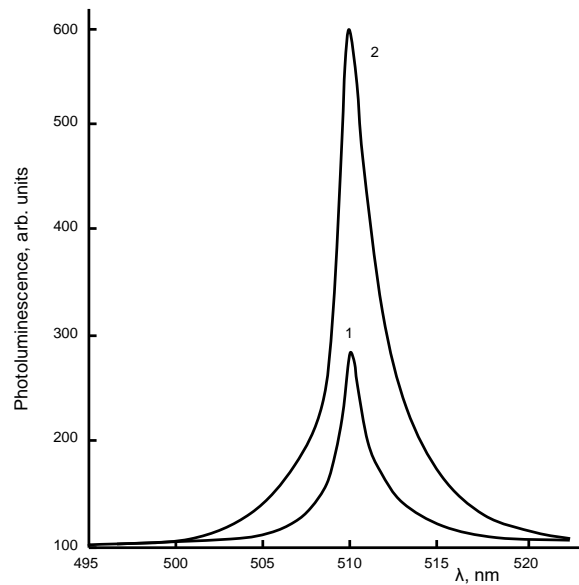


Fig.6. Photoluminescence spectra of CdTe nanoparticles at two different excitation powers, the second harmonic of a neodymium laser ( $\hbar\omega = 2.34$  eV): 1 – 1 MW/cm<sup>2</sup>; 2 – 10 MW/cm<sup>2</sup>.

Figure 6 shows the photoluminescence spectra of CdTe nanoparticles excited by the second harmonic of the Nd:YAG laser ( $\hbar\omega = 2.34$  eV). As can be seen from the figure, the emission maximum of nanoparticles corresponds to wavelengths ~ 510 nm (2.43 eV). An increase in the laser light power by 1.2 times does not affect the position of the spectra, but leads to an increase in the radiation intensity by ~2.1 times.

As regards the nature of the observed radiations, in our opinion they are due to the radiative recombination of free excitons. Knowing the energy of free excitons in CdTe

( $E_{ex} \sim 29$  meV), it is possible to determine the band gap of nanoparticles  $E_g = h\nu + E_{fr.ex.}$ , which is equal to 2.46 eV, which is in satisfactory agreement with the value determined from the absorption spectrum.

### 3. CONCLUSION

A new method for synthesizing CdTe nanoparticles by laser radiation is proposed. Highly

pure CdCl<sub>2</sub> and TeO<sub>2</sub> powders mixed with distilled water were used as initial raw materials. The ablation process was performed by laser radiation with a wavelength of 1064 nm, with a pulse energy of 135 mJ and an ablation time of ~10 min. Under these ablation conditions in a colloidal solution, the

formation of nanoparticles with diameters from ~10 to ~50 nm was observed. It is shown that the synthesized nanoparticles retain the crystalline structure of the bulk material and emit photoluminescence at 510 nm associated with the radiative recombination of free excitons.

- 
- [1] *N.G. Semaltianos, S. Logothetidis, W. Perrie, S. Romani, R.J. Potter, M. Sharp, G. Dearden and*
- [2] *K.G. Watkins.* CdTe nanoparticles synthesized by laser ablation. *Applied physics letters.* 95, 2009, 033301-033306.
- [3] *M. Gao, S. Kirstein, H. Möhwald, A.L. Rogach, A. Kornowski, A. Eychmüller, and H. Weller.* Strongly photoluminescent CdTe nanocrystals by proper surface modification. *J. Phys. Chem. B* 102, 1998, 8360.
- [4] *L. Rogach.* Nanocrystalline CdTe and CdTe(S) particles: Wet chemical preparation, size-dependent optical properties and perspectives of optoelectronic applications. *Mater. Sci. Eng., B* 69, 2000, 435.
- [5] *A.V. Bulgakov, A.B. Yevtushenko, Yu.Q. Shukhov, I. Ozerov, V. Marin.* «Quantum electronics», 40, № 11, 2010, 1021-1033.
- [6] *Y. Luo, T. Tan, S. Wang, R. Pang, L. Jiang, D. Li, J. Feng, H. Zhang, S. Zhang, Ch. Li.* Ligand-Induced Nucleation Growth Kinetics of CdTe QDs: Implications for White-Light-Emitting Diodes. *ACS Applied Nano Materials.* 5 (1), 2022, 401.
- [7] *H. Haug, S.W. Koch.* Quantum Theory of the Optical and Electronic Properties of Semiconductors. Singapore: World Scientific Publishing, 1994.
- [8] *A. Morales-Acevedo.* Thin film CdS/CdTe solar cells: research perspectives. *Solar Energy,* 80, 2006, 675.
- [9] *K. Zweibel.* Engineering. The impact of tellurium supply on cadmium telluride photovoltaics. *Science,* 328, 2010, 699.
- [10] *R.L. Johnston.* Atomic and Molecular Clusters. London: CRC Press, 2002. 256.
- [11] *B.M. Smirnov.* Generation of cluster beams. *Advances in the physical sciences,* 173, 2003, 609.
- [12] *Q.N. Makarov.* Extremal processes in clusters in collision with a solid surface. *Advances in the physical sciences,* 176, 2006, 121.
- [13] *C.B. Murray, D.J. Norris, and M.G. Bawendi.* Synthesis and characterization of nearly monodisperse CdE (E = sulfur, selenium, tellurium) semiconductor nanocrystallites. *J. Am. Chem. Soc.* 115, 1993, 8706.
- [14] *L. Rogach, L. Katsikas, A. Kornowski, D. Su, A. Eychmüller, and H. Weller, Ber. Bunsenges.* Synthesis, morphology and optical properties of thiol-stabilized CdTe nanoclusters in aqueous solution. *Phys. Chem.* 101, 1997, 1668.
- [15] *Z.A. Peng and X. Peng.* Formation of High-Quality CdTe, CdSe, and CdS Nanocrystals Using CdO as Precursor. *J. Am. Chem. Soc.* 123, 2001, 183.
- [16] *G. Dance, A. Choy, and M.L. Scudder.* Syntheses, properties, and molecular and crystal structures of (Me<sub>4</sub>N)<sub>4</sub>[E<sub>4</sub>M<sub>10</sub>(SPh)<sub>16</sub>] (E = sulfur or selenium; M = zinc or cadmium): molecular supertetrahedral fragments of the cubic metal chalcogenide lattice. *J. Am. Chem. Soc.* 106, 1984, 6285.
- [17] *M. Marc-Oliver Piepenbrock, Tom Stirner, Mary O'Neill and Stephen M. Kelly.* Growth dynamics of CdTe nanoparticles in liquid and crystalline phases. *J. Am. Chem. Soc.* 129, 24, 2007, 7674.
- [18] *Martin Sharp.* CdTe nanoparticles synthesized by laser ablation. *Applied Physics Letters.* 95, 2009, 033302.
- [19] *A.R. Albert, A.Y. John.* Colloids and Surfaces A: Physicochemical and Engineering Aspects . 279, 1-3, 2006, 121.
- [20] *L. Patrone, D. Nelson, V.I. Safarov, M. Sentis, W.J. Marine.* Photoluminescence of silicon nanoclusters with reduced size dispersion produced by laser ablation. *Appl. Phys.,* 87, 2000, 3829.
- [21] *T. Seto, T. Orii, M. Hirasawa, N. Aya.* Fabrication of silicon nanostructured films by deposition of size-selected nanoparticles generated by pulsed laser ablation. *Thin Solid Films,* 437, 2003, 230.
- [22] *B. Lukyanchuk, W. Marine.* On the delay time in photoluminescence of Si-nanoclusters, produced by laser ablation. *Appl. Surf. Sci.,* 314, 2000, 154.
- [23] *S.I. Anisimov, B.S. Lukyanchuk.* Selected problems of the theory of laser ablation. *Advances in the physical sciences,* 172, 2002, 301.
- [24] *A.V. Bulgakov, I. Ozerov, W. Marine.* Silicon clusters produced by femtosecond laser ablation: non-thermal emission and gas-phase condensation. *Appl. Phys. A,* 79, 2004, 1591.
- [25] *S. Xu, J. Ziegler, T.J. Nann.* Rapid synthesis of highly luminescent InP and InP/ZnS nanocrystals. *Mater. Chem.,* 18, 2008, 2653.
- [26] *I. Ozerov, D. Nelson, A.V. Bulgakov, W. Marine, M. Sentis.* Synthesis and laser processing of ZnO nanocrystalline thin films. *Appl. Surf. Sci.,* 349, 2003, 212.
- [27] *S. Neretina, P. Mascher, R.A. Hughes, N. Braidy, W.H. Gong, J.F. Britten, J.S. Preston, N.V. Sochinskii, P. Dippo.* Evolution of wurtzite CdTe through the formation of cluster assembled films. *Appl. Phys. Lett.,* 89, 2006, 133101.

- [28] *J. Bonse, M. Munz, H.J. Sturm.* Structure formation on the surface of indium phosphide irradiated by femtosecond laser pulses. *Appl. Phys.*, 97, 2005, 013538.
- [29] JCPDS, International Centre for Diffraction Data, USA, Card Number 15-0770. S. Samuel. Nanolasers: lasing from nanoscale quantum wires *Int. J. of Nanotechnology* 1, 2004, 42-85.

*Received: 10.07.2023*